

Requirement of Ala Residues at g Position in Heptad Sequence of α -Helix-forming Peptide for Formation of Fibrous Structure

Gaku Aoki¹, Toyo K. Yamada¹, Mayu Arii², Shuichi Kojima^{2,*} and Tadashi Mizoguchi¹¹Department of Physics; and ²Institute for Biomolecular Science, Faculty of Science, Gakushuin University, Mejiro, Tokyo 171-8588, Japan

Received March 4, 2008; accepted April 8, 2008; published online April 16, 2008

One feature of the α 3-peptide, which has the amino acid sequence of (Leu-Glu-Thr-Leu-Ala-Lys-Ala)₃, that distinguishes it from many other α -helix-forming peptides is its ability to form fibrous assemblies that can be observed by transmission electron microscopy. In this study, the effects of Ala→Gln substitution at the e (5th) or g (7th) position in the above heptad sequence of the α 3-peptide on the formation of α -helix and fibrous assemblies were investigated by circular dichroism spectral measurement and atomic force microscopy. The 5Q α 3-peptide obtained by Ala→Gln substitution at the e position of the α 3-peptide was found to form very short fibrils with long-elliptical shape, whereas the 7Q α 3-peptide with Gln residues at the g position lost its ability to form such assemblies, in spite of α -helix formation in both peptides; the stabilities of both peptides decreased. These results indicate that Ala residues at the g position in the heptad sequence of the α 3-peptide are key residues for the formation of fibrous assemblies, which may be due to hydrophobic interactions between α -helical bundle surfaces.

Key words: α -helix, atomic force microscopy, circular dichroism spectra, fibre formation, heptad sequence.

Abbreviations: AFM, atomic force microscopy; TEM, transmission electron microscopy.

The α -helix is a secondary structure of proteins that contributes to the stability and folding of proteins. Its sequence-stability relationship, as well as several interactions between side chains and the intrinsic helix-forming tendency of amino acids, has been extensively studied (1–19). We previously designed and synthesized an amphipathic 21-residue peptide (α 3-peptide) with three repeats of the seven-residue (heptad) sequence Leu-Glu-Thr-Leu-Ala-Lys-Ala, anticipating that it will form an α -helical bundle structure through hydrophobic interactions between Leu residues. We found that the α 3-peptide exhibits a concentration-dependent stabilization of its α -helix, suggesting the formation of oligomers (20). Unexpectedly, we demonstrated that the α 3-peptide form fibrous assemblies that can be observed by transmission electron microscopy (TEM) (21). To our knowledge, this might have been the first report on the formation of fibrous assemblies by a *de novo*-designed α -helical short peptide, in contrast to many reports on the formation of amyloid mainly composed of β -sheets (22–31). Thus, we have synthesized several variants of the α 3-peptide to investigate the relationship between the sequence, α -helix stability and formation of fibrous assemblies. When the sequence of the α 3-peptide was reversed, the resultant r3-peptide formed a very stable α -helix and long fibres (32). Since the α -helix, which does not form fibrous assemblies, is generally destabilized by sequence reversal through electrostatic repulsion with an intrinsic

dipole of the α -helix, the stabilization of the α 3-peptide by sequence reversal may be specific to only fibre-forming peptides. On the other hand, the α -helix and fibrous assemblies of the α 3-peptide are destabilized by substitutions of Leu residues on the hydrophobic surface with less hydrophobic amino acids, possibly owing to the decrease in the degree of hydrophobic interactions (33). This is a general feature of peptides that form multimeric α -helical bundle structures.

In this study, we focused on Ala residues at the e (5th) and g (7th) positions in the heptad sequence of the α 3-peptide. Since peptides with charged residues (Glu and Lys) at these two positions form a two-stranded coiled-coil structure (11, 14), it is suggested that Ala residues at both or either position in the α 3-peptide are required for the formation of fibrous structures. Thus, we substituted these Ala residues of the α 3-peptide with less hydrophobic Gln residues, since Gln is a polar amino acid with the strongest α -helix-forming tendency among non-charged and non-hydrophobic amino acids.

α 3-peptide variants with Gln residues at the e or g position in the heptad sequence of the α 3-peptide, namely the 5Q α 3- and 7Q α 3-peptides (Fig. 1), respectively, were chemically synthesized and purified using reverse-phase HPLC with an acetonitrile gradient in 0.1% trifluoroacetic acid. Their concentrations were determined by amino acid composition analysis after hydrolysis with 5.7 N HCl at 110°C for 24 h *in vacuo*.

The CD spectra of the 5Q α 3- and 7Q α 3-peptides were measured using a JASCO J-720 spectropolarimeter in a neutral pH buffer at 30°C to investigate the effects of Ala→Gln substitutions at the e or g position in the

*To whom correspondence should be addressed. Tel: +81-3-3986-0221, ext. 6505, Fax: +81-3-5992-1034, E-mail: shuichi.kojima@gakushuin.ac.jp

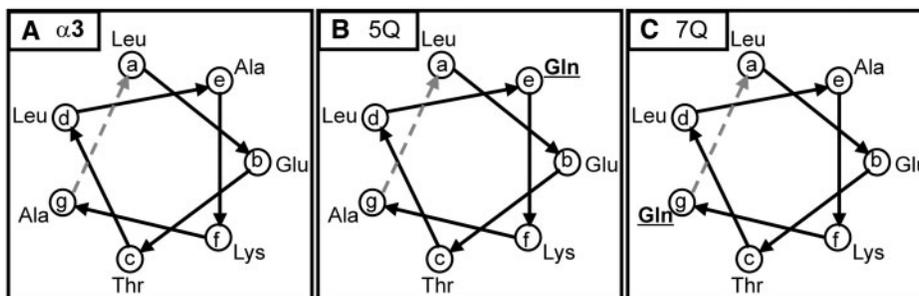


Fig. 1. Helical wheel representations of (A) $\alpha 3$ -, (B) $5Q\alpha 3$ - and (C) $7Q\alpha 3$ -peptides. The $5Q\alpha 3$ - or $7Q\alpha 3$ -peptide was produced by substituting Ala residues at the e (5th) or g (7th) position in the heptad sequence of the $\alpha 3$ -peptide.

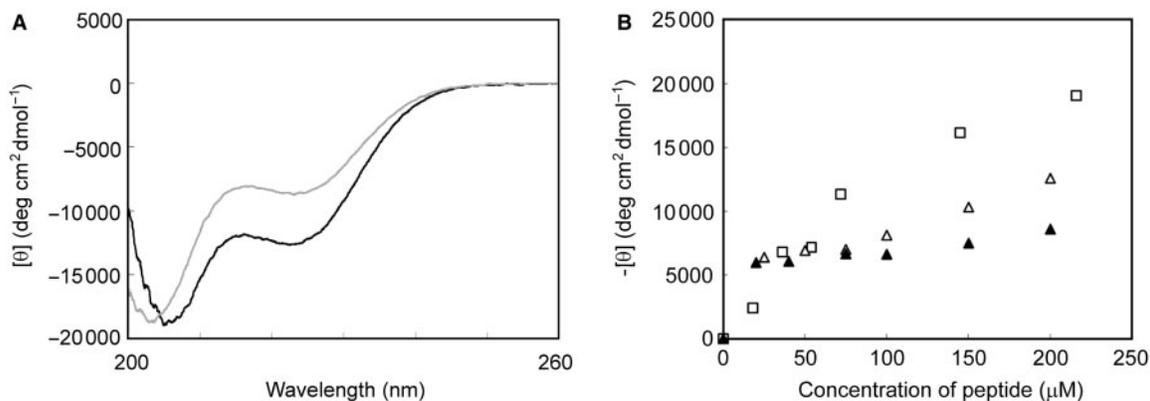


Fig. 2. (A) CD spectra of $5Q\alpha 3$ -peptide (black line) and $7Q\alpha 3$ -peptide (gray line) at $200\ \mu\text{M}$ and (B) peptide concentration dependence of $[\theta]$ at $222\ \text{nm}$ of the $\alpha 3$ -peptide (open square), $5Q\alpha 3$ -peptide (open triangle) and $7Q\alpha 3$ -peptide (filled triangle) in $10\ \text{mM}$ phosphate buffer (pH 6.0) containing $0.1\ \text{M}$ KCl. After the concentrations

of the peptides were determined by amino acid composition analyses, the CD spectra at various peptide concentrations were measured at 30°C using a JASCO J-720 circular dichroism spectropolarimeter with a path length of $1\ \text{mm}$; the results are expressed as mean residue molar ellipticity.

heptad sequence of the $\alpha 3$ -peptide on the α -helix stability of the $\alpha 3$ -peptide. It was found that both peptides showed CD spectra that indicate α -helix formation (Fig. 2A), as in the case of other variants of the $\alpha 3$ -peptide. However, since the helix contents of both peptides were lower than that of the $\alpha 3$ -peptide, the concentration dependences of $[\theta]$ at $222\ \text{nm}$ for the two peptides were investigated and compared with that of the $\alpha 3$ -peptide.

As shown in Fig. 2B, the $[\theta]$ values of the $5Q\alpha 3$ - and $7Q\alpha 3$ -peptides increased as peptide concentration increased, which strongly indicates that the α -helices of these peptides are stabilized by oligomerization, as in the case of other variants of the $\alpha 3$ -peptide. However, the α -helix of the $\alpha 3$ -peptide was destabilized by the substitution of Ala residues at the e position in the heptad sequence with Gln residues, and much more prominently by the substitution at the g position. As a result, among the peptides examined, the $7Q\alpha 3$ -peptide had the most unstable α -helix. The helix contents of the $\alpha 3$ -, $5Q\alpha 3$ - and $7Q\alpha 3$ -peptides at about $200\ \mu\text{M}$, which were estimated using the equation $[\theta]_{222\ \text{nm}}/(-40,000(1-2.5/n)+100T)$, where $n=21$ and $T=30$ (34), were 59, 39 and 27%, respectively.

Since the $\alpha 3$ -peptide was demonstrated to form fibrils $5\text{--}10\ \text{nm}$ in width and intermediate in length that can be

observed by TEM in a neutral pH buffer, we observed such fibrous structures of the $\alpha 3$ -peptide in air at 20°C by atomic force microscopy (AFM, JEOL-JSTM-4200D), as well as those of the $5Q\alpha 3$ - and $7Q\alpha 3$ -peptides to determine the effects of Ala \rightarrow Gln substitution in the $\alpha 3$ -peptide on the formation of fibrous assemblies. AFM in the tapping mode was performed with Si cantilevers (spring constant: $1.38\ \text{N/m}$, resonance frequency: $74\ \text{kHz}$) on an atomically flat cleaved mica (001) surface immersed in $20\ \mu\text{l}$ of peptide solutions. The typical scan speed was about $3\ \text{min/image}$.

Figures 3A and B–D show AFM images of the $\alpha 3$ -peptide at 4 and $50\ \mu\text{M}$, in phosphate buffer with pHs $5\text{--}6$. No fibrous structures were observed at pH 2 , 7 or 8 . It is clear that the $\alpha 3$ -peptide at $50\ \mu\text{M}$ formed fibrils as demonstrated by TEM, whereas at $4\ \mu\text{M}$ no such fibrous assemblies were observed. Fibrils were observed between pHs 3 and 6 . Each single fibril had a length of $>1,000\ \text{nm}$. At pH 5.5 , each fibril had a width of 33.0 ± 0.4 and $2.1 \pm 0.4\ \text{nm}$ in height.

When the $5Q\alpha 3$ - and $7Q\alpha 3$ -peptides at $40\ \mu\text{M}$ were observed by AFM, no fibrous assemblies were observed. Since the α -helices of these peptides were less stable than that of the $\alpha 3$ -peptide, as demonstrated by CD measurements, AFM was carried out at higher peptide

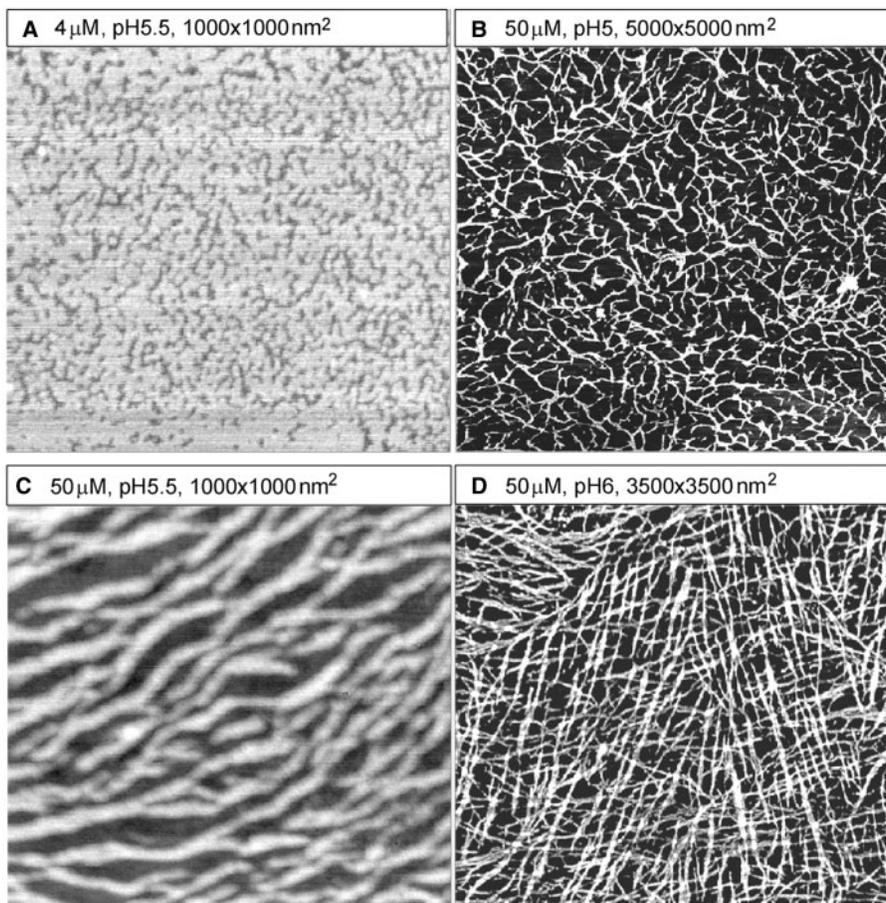


Fig. 3. AFM images of the $\alpha 3$ -peptide from 4 μM solution at pH 5.5 (A) and from 50 μM solution at pHs 5 (B), 5.5 (C) and 6 (D). A single fibre has a length of >1000 nm.

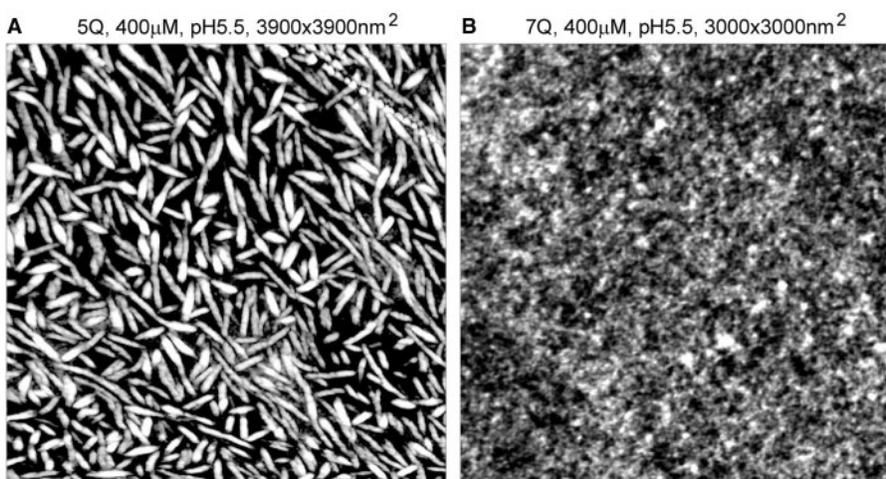


Fig. 4. AFM images of the 5Q $\alpha 3$ -peptide (A) and 7Q $\alpha 3$ -peptide (B) from 400 μM solution.

concentrations. When the concentration of the 5Q $\alpha 3$ -peptide was increased up to 400 μM , many very short fibrils with long-elliptical shape were detected, as shown in Fig. 4A. Each single 5Q $\alpha 3$ -peptide fibril was 400 ± 100 nm in length, 2.9 ± 0.8 nm in height and 61.7 ± 8.5 nm

in width. However, no such structures were observed for the 7Q $\alpha 3$ -peptide at the same peptide concentration (Fig. 4B). These results strongly indicate that Ala residues at the g position of the heptad sequence of the $\alpha 3$ -peptide largely contribute to the formation of fibrous assemblies.

The destabilization of the α -helix formed by the 5Q α 3-peptide is considered to be due to the difference in α -helix formation tendency between Gln and Ala. However, since some degree of hydrophobicity is retained in the 5Q α 3-peptide, very short fibrils with long-elliptical shape of this peptide might have been observed by AFM, although a higher peptide concentration was required for such observation. In contrast, the 7Q α 3-peptide that also has Gln residues did not form fibrous assemblies. To explain this phenomenon, we considered that the chemical environments around the Gln residues in the helical bundle structure differed between the 5Q α 3- and 7Q α 3-peptides. From the helical wheel representation (Fig. 1), the surface formed by c-, d- and g-position residues is more hydrophobic than the opposite surface formed by a-, b- and e-position residues, since a Thr residue with methyl and hydroxyl groups is more hydrophobic than a Glu residue with a negative charge. Therefore, the 5Q α 3-peptide that retains a more hydrophobic surface is considered to have an ability to form supramolecular assemblies, whereas the 7Q α 3-peptide in which the hydrophobicity of the surface formed by c-, d- and g-position residues is weakened by Ala \rightarrow Gln substitution at the g position seems to lose its ability to form such assemblies. Zeng *et al.* (35) have previously produced various e- and g-position mutants of a two-stranded GCN4 leucine zipper by random mutagenesis and have shown that type II mutants that form higher order oligomers commonly have Ala residues at the g position. Their finding is consistent with our results in this study. Therefore, similar mechanisms of forming higher order oligomers may operate in their peptides and ours; however, they provided no explanation for their finding.

It is also demonstrated that a decrease in the hydrophobicity of the helical surface formed by c-, d- and g-position residues of the α 3-peptide by Leu \rightarrow Val substitution at the d position results in the loss of the ability to form fibrous assemblies (33). However, in this case, the resultant peptide (4V α 3-peptide) also had no ability to form α -helices; thus, the formation of fibrous assemblies is closely related to α -helix formation. In contrast, the 7Q α 3-peptide in this study lost its ability to form fibrous assemblies in spite of retaining its ability for α -helix formation. Therefore, Ala residues at the g position in the α 3-peptide are concluded to be the key residues for forming fibrous assemblies. In the future, subsequent analyses using α 3-derived peptides with various sequences will clarify the detailed mechanisms of the fibre formation of the α 3-peptide.

REFERENCES

- Acharya, A., Rishi, V., and Vinson, C. (2006) Stability of 100 homo and heterotypic coiled-coil a-a' pairs for ten amino acids (A, L, I, V, N, K, S, T, E, and R). *Biochemistry* **45**, 11324–11332
- Chakrabartty, A., Kortemme, T., and Baldwin, R.L. (1994) Helix propensities of the amino acids measured in alanine-based peptides without helix-stabilizing side-chain interactions. *Protein Sci.* **3**, 843–852
- Doig, A.J. and Baldwin, R.L. (1995) N- and C-capping preferences for all 20 amino acids in α -helical peptides. *Protein Sci.* **4**, 1325–1336
- Horovitz, A., Mathews, J.M., and Fersht, A.R. (1992) α -helix stability in proteins. II. Factors that influence stability at an internal position. *J. Mol. Biol.* **227**, 560–568
- Kohn, W.D., Kay, C.M., and Hodges, R.S. (1998) Orientation, positional, additivity, and oligomerization-state effects of interhelical ion pairs in α -helical coiled-coils. *J. Mol. Biol.* **283**, 993–1012
- Kwok, S.C. and Hodges, R.S. (2003) Clustering of large hydrophobes in the hydrophobic core of two-stranded α -helical coiled-coils controls protein folding and stability. *J. Biol. Chem.* **278**, 35248–35254
- Lumb, K.J. and Kim, P.S. (1995) A buried polar interaction imparts structural uniqueness in a designed heterotrimeric coiled coil. *Biochemistry* **34**, 8642–8648
- Lyu, P.C., Liff, M.L., Marky, L.A., and Kallenbach, N.R. (1990) Side chain contributions to the stability of alpha-helical structure in peptides. *Science* **250**, 669–673
- Matousek, W.M., Ciani, B., Fitch, C.A., Garcia-Moreno, B., Kammerer, R.A., and Alexandrescu, A.T. (2007) Electrostatic contributions to the stability of the GCN4 leucine zipper structure. *J. Mol. Biol.* **374**, 206–219
- Moitra, J., Szilak, L., Krylov, D., and Vinson, C. (1997) Leucine is the most stabilizing aliphatic amino acid in the d position of a dimeric leucine zipper coiled coil. *Biochemistry* **36**, 12567–12573
- Monera, O.D., Kay, C.M., and Hodges, R.S. (1994) Electrostatic interactions control the parallel and antiparallel orientation of α -helical chains in two-stranded α -helical coiled coils. *Biochemistry* **33**, 3862–3871
- Monera, O.D., Zhou, N.E., Lavigne, P., Kay, C.M., and Hodges, R.S. (1996) Formation of parallel and antiparallel coiled-coils controlled by the relative positions of alanine residues in the hydrophobic core. *J. Biol. Chem.* **271**, 3995–4001
- Oakley, M.G. and Kim, P.S. (1998) A buried polar interaction can direct the relative orientation of helices in a coiled coil. *Biochemistry* **37**, 12603–12610
- O'Shea, E.K., Rutkowski, R., and Kim, P.S. (1989) Evidence that the leucine zipper is a coiled coil. *Science* **243**, 538–542
- Padmanabhan, P. and Baldwin, R.L. (1994) Tests for helix-stabilizing interactions between various nonpolar side chains in alanine-based peptides. *Protein Sci.* **3**, 1992–1997
- Padmanabhan, P., York, E.J., Stewart, J.M., and Baldwin, R.L. (1996) Helix propensities of basic amino acids increase with the length of the side-chain. *J. Mol. Biol.* **257**, 726–734
- Petukhov, M., Munoz, V., Yumoto, N., Yoshikawa, S., and Serrano, L. (1998) Position dependence of non-polar amino acid intrinsic helical propensities. *J. Mol. Biol.* **278**, 279–289
- Tripet, B., Wagschal, K., Lavigne, P., Mant, C.T., and Hodges, R.S. (2000) Effects of side-chain characteristics on stability and oligomerization state of a *de novo*-designed model coiled-coil: 20 amino acid substitutions in position "d". *J. Mol. Biol.* **300**, 377–402
- Wagschal, K., Tripet, B., Lavigne, P., Mant, C., and Hodges, R.S. (1999) The role of position a in determining the stability and oligomerization state of α -helical coiled coils: 20 amino acid stability coefficients in the hydrophobic core of proteins. *Protein Sci.* **8**, 2312–2329
- Kojima, S., Kuriki, Y., Sato, Y., Arisaka, F., Kumagai, I., Takahashi, S., and Miura, K. (1996) Synthesis of α -helix-forming peptides by gene engineering methods and their characterization by circular dichroism spectra measurements. *Biochim. Biophys. Acta.* **1294**, 129–137
- Kojima, S., Kuriki, Y., Yoshida, T., Yazaki, K., and Miura, K. (1997) Fibril formation by an α -helix-forming polypeptides produced by gene engineering. *Proc. Jpn Acad.* **73B**, 7–11
- Frare, E., Mossuto, M.F., de Laureto, P.P., Dumoulin, M., Dobson, C.M., and Fontana, A. (2006) Identification of the

- core structure of lysozyme amyloid fibrils by proteolysis. *J. Mol. Biol.* **361**, 551–561
23. Fezoui, Y., Hartley, D.M., Walsh, D.M., Selkoe, D.J., Osterhout, J.J., and Teplow, D.B. (2000) A *de novo* designed helix-turn-helix peptide forms nontoxic amyloid fibrils. *Nat. Struct. Biol.* **7**, 1095–1099
 24. Iwata, K., Fujiwara, T., Matsuki, Y., Akutsu, H., Takahashi, S., Naiki, H., and Goto, Y. (2006) 3D structure of amyloid protofilaments of β 2-microglobulin fragment probed by solid-state NMR. *Proc. Natl Acad. Sci. USA* **103**, 18119–18124
 25. Jiménez, J.L., Nettleton, E.J., Bouchard, M., Robinson, C.V., Dobson, C.M., and Saibil, H.R. (2002) The protofilament structure of insulin amyloid fibrils. *Proc. Natl Acad. Sci. USA* **99**, 9196–9201
 26. Kajava, A.V., Aebi, U., and Steven, A.C. (2005) The parallel superpleated beta-structure as a model for amyloid fibrils of human amylin. *J. Mol. Biol.* **348**, 247–252
 27. Kammerer, R.A., Kostrewa, D., Zurdo, J., Detken, A., Garcia-Echeverria, C., Green, J.D., Müller, S.A., Meier, B.H., Winkler, F.K., Dobson, C.M., and Steinmetz, M.O. (2004) Exploring amyloid formation by a *de novo* design. *Proc. Natl Acad. Sci. USA* **101**, 4435–4440
 28. Kammerer, R.A. and Steinmetz, M.O. (2006) *De novo* design of a two-stranded coiled-coil switch peptide. *J. Struct. Biol.* **155**, 146–153
 29. Lührs, T., Ritter, C., Adrian, M., Riek-Loher, D., Bohrmann, B., Döbeli, H., Schubert, D., and Riek, R. (2005) 3D structure of Alzheimer's amyloid- β (1-42) fibrils. *Proc. Natl Acad. Sci. USA* **102**, 17342–17347
 30. Nelson, R., Sawaya, M., Balbirnie, M., Madsen, A.Ø, Riek, C., Grothe, R., and Eisenberg, D. (2005) Structure of the cross- β spine of amyloid-like fibrils. *Nature* **435**, 773–778
 31. Yagi, H., Ban, T., Morigaki, K., Naiki, H., and Goto, Y. (2007) Visualization and classification of amyloid β supra-molecular assemblies. *Biochemistry* **46**, 15009–15017
 32. Kojima, S., Kuriki, Y., Yazaki, K., and Miura, K. (2005) Stabilization of the fibrous structure of an α -helix-forming peptide by sequence reversal. *Biochem. Biophys. Res. Commun.* **331**, 577–582
 33. Takei, T., Okonogi, A., Tateno, K., Kimura, A., Kojima, S., Yazaki, K., and Miura, K. (2006) The effects of the side chains of hydrophobic aliphatic amino acid residues in an amphipathic polypeptide on the formation of α helix and its association. *J. Biochem* **139**, 271–278
 34. Scholtz, J.M., Qian, H., York, E.J., Stewart, J.M., and Baldwin, R.L. (1991) Parameters of helix-coil transition theory for alanine-based peptides of varying chain lengths in water. *Biopolymers* **31**, 1463–1470
 35. Zeng, X., Zhu, H., Lashuel, H.A., and Hu, J.C. (1997) Oligomerization properties of GCN4 leucine zipper e and g position mutants. *Protein Sci.* **6**, 2218–2226